

Improved large-mode area endlessly single-mode photonic crystal fibers

N. A. Mortensen,* M. D. Nielsen,*† J. R. Folkenberg,* A. Petersson,* and H. R. Simonsen*

*Crystal Fibre A/S, Blokken 84, DK-3460 Birkerød, Denmark

†Research Center COM, Technical University of Denmark, DK-2800 Kongens Lyngby, Denmark

We numerically study the possibilities for improved large-mode area endlessly single mode photonic crystal fibers for use in high-power delivery applications. By carefully choosing the optimal hole diameter we find that a triangular core formed by three missing neighboring air holes considerably improves the mode area and loss properties compared to the case with a core formed by one missing air hole. In a realized fiber we demonstrate an enhancement of the mode area by $\sim 30\%$ without a corresponding increase in the attenuation.

Applications requiring high-power delivery call for single-mode large-mode area (LMA) optical fibers. While standard-fiber technology has difficulties in meeting these requirements the new class[1] of all-silica photonic crystal fibers (PCF) has a big potential due to their endlessly single-mode properties [2] combined with (in principle) unlimited large effective areas.[3] For recent reviews we refer to Refs. 4, 5.

The cladding structure of these PCFs consists of a triangular array of air holes of diameter d and pitch Λ corresponding to an air-filling fraction $f = \pi/(2\sqrt{3})(d/\Lambda)^2$. The presence of the air holes results in a strongly wavelength dependent effective index n_{eff} of the cladding and in the short and long wavelength limits we have

$$\lim_{\lambda \ll \Lambda} n_{\text{eff}} = n_{\text{si}}, \quad \lim_{\lambda \gg \Lambda} n_{\text{eff}} = f \times n_{\text{air}} + (1 - f) \times n_{\text{si}} \equiv \bar{n}. \quad (1)$$

The numerical results in the intermediate regime can be reasonably fitted by *e.g.*

$$n_{\text{eff}} \approx \bar{n} + (n_{\text{si}} - \bar{n}) \cosh^{-2}(\alpha \lambda / \Lambda) \quad (2)$$

with α of order unity and only weakly dependent on d/Λ , see Fig. 1. It is these unusual dispersion properties of the cladding which facilitate design of large-mode area endlessly single-mode optical fibers.[2, 3]

In order to confine the light to a core region of high index a defect in the triangular air-hole array is introduced. Normally this is done by leaving out one of the air holes. In the stack-and-pull approach [1] one of the capillaries is replaced by a silica rod, see left insert of Fig. 3. By choice the index of the defect can be raised by various doping and depressed-index core has also been studied recently.[6]

The single-rod PCF can in principle be kept endlessly single-mode no matter how large a core diameter.[3] However, when scaling-up the fibre-structure the mode area is increased at the cost of an increased susceptibility to longitudinal modulations [7] such as *e.g.* micro-bending [8] and macro-bending [9] induced scattering loss. The reason is that in order to increase the mode area the pitch Λ is scaled to a large value, but this also implies that $\lambda/\Lambda \ll 1$ and in this limit the core index approaches the cladding index, see Eq. (1). Fig. 1 suggests that

the decreasing index step may be compensated by increasing the air hole diameter, which can be done up to $d/\Lambda \sim 0.45$ which is the upper limit for endlessly single-mode operation. For a discussion of the particular number see *e.g.* Refs. 10, 11, 12. For LMA PCFs working in the UV and visible regimes this sets an upper limit on the mode areas that can be realized with a reasonable loss and many applications call for an improved LMA PCF design.

The inclusion of more than a single solid rod in the stacking has been used to form multiple-core [13] and highly birefringent PCFs.[14] In this work we demonstrate how inclusion of more neighboring solid rods can be used for improved LMA endlessly single-mode PCFs. Intuitively this may not seem to be a promising direction since a reduced value of d/Λ is needed to keep the PCF endlessly single-mode. For the birefringent case with two neighboring rods[14] the limit is $d/\Lambda \sim 0.30$ and for a tri-

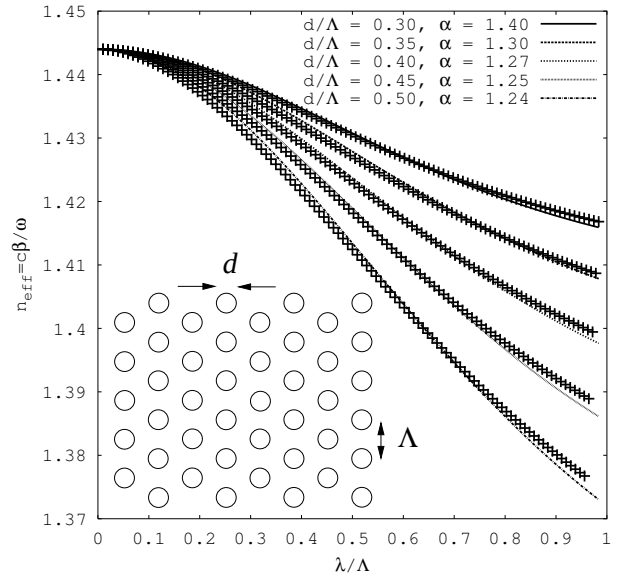


FIG. 1: Effective cladding index for the triangular cladding structure with different hole diameters. The points show numerical results from a fully-vectorial calculation and the solid lines are fits to Eq. (2) with α as fitting parameter.

angular core formed by three neighboring rods (see right insert of Fig. 3) we have found $d/\Lambda \sim 0.25$ as the upper limit for endlessly single-mode operation. However, for a given desired mode area this decrease in d/Λ is compensated for by a corresponding smaller value of Λ . In fact, the edge-to-edge separation $\Lambda - d$ of the holes turns out to be the important length scale rather than the pitch Λ itself.

In introducing a multiple number of rods an important question about possible birefringence arises. The structure with a single rod has a six-fold symmetry and though group theory clearly excludes any intrinsic birefringence [15] there has been quite some debate based on numerical studies, see *e.g.* Ref. 16 and references therein. More generally, group theory predicts that for m -fold rotational symmetry and $m > 2$ a mode with a preferred direction is one of a pair, see Ref. 15 and references therein. PCFs with a triangular core formed by three neighboring rods have a 3-fold symmetry and thus no intrinsic birefringence. The non-birefringent property is also confirmed numerically using a fully-vectorial plane-wave method [17] and any small numerical birefringence originates from a numerical grid with symmetry different from the dielectric structure being studied.

In order to compare the single-rod and three-rod PCFs we study two quantities; *i*) the mode-field diameter MFD and *ii*) the coupling length ζ to the cladding. We relate the MFD to the effective area [11]

$$A_{\text{eff}} = \left[\int d\mathbf{r}_{\perp} I(\mathbf{r}_{\perp}) \right]^2 \left[\int d\mathbf{r}_{\perp} I^2(\mathbf{r}_{\perp}) \right]^{-1}, \quad (3)$$

by $A_{\text{eff}} = \pi(\text{MFD}/2)^2$. Here, $I(\mathbf{r}_{\perp})$ is the transverse intensity distribution of the fundamental mode. For a Gaussian mode of width w Eq. (3) gives $\text{MFD} = 2w$ and the intensity distribution in the types of PCF studied in this work can be considered close to Gaussian [11, 18] as we also confirm experimentally.

The coupling length (beat length)

$$\zeta = 2\pi/(\beta - \beta_{\text{cl}}) \quad (4)$$

between the fundamental mode and the cladding (radiation field) can be used in formulating a low-loss criterion. [19] The additional competing length scales consist of the wavelength and the length scale L_n (or as set $\{L_n\}$ of length scales) for nonuniformity along the fiber and loss will be significant when

$$\lambda \lesssim L_n \lesssim \zeta \quad (5)$$

and otherwise loss can be expected to be small. Thus, the shorter a coupling length the lower susceptibility to longitudinal modulations. We emphasize that this criterion does not quantify loss, but it gives a correct parametric dependence of loss for various loss mechanisms. For PCFs the relevance of this criteria was recently confirmed experimentally in the case of macro-

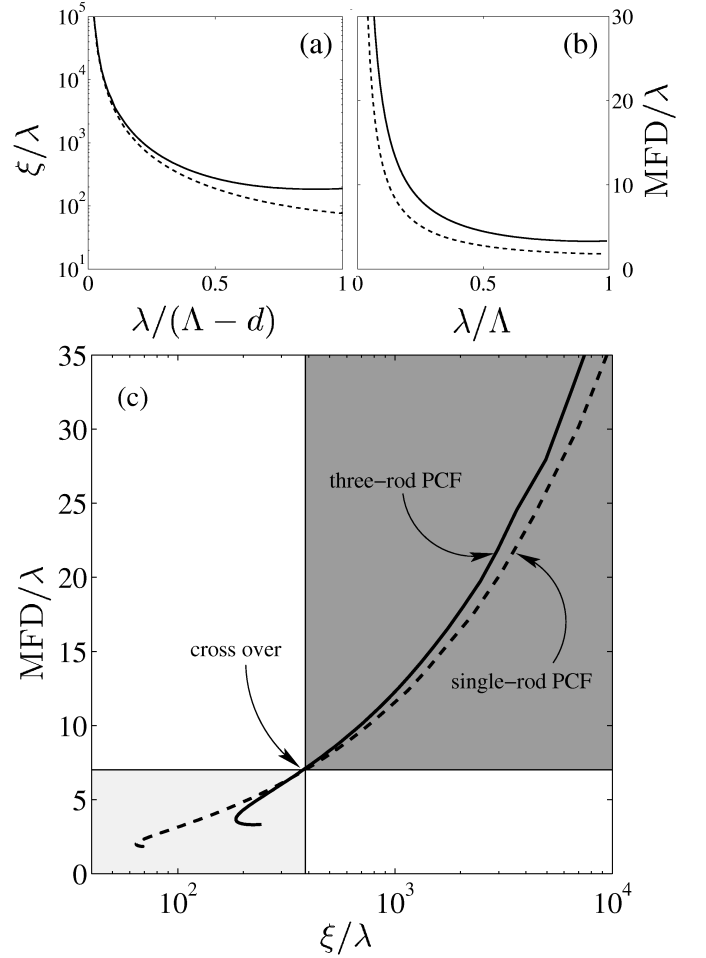


FIG. 2: Comparison of the single-rod (dashed lines) and three-rod (solid lines) PCFs with $d/\Lambda = 0.45$ and 0.25 , respectively. Panel (a) shows the coupling length versus wavelength and panel (b) shows the mode-field diameter as a function of wavelength. In panel (c) the results of panels (a) and (b) are combined to a plot of mode-field diameter versus coupling length.

bending [7] and micro-bending [8] induced nonuniformities and also in a study of PCFs with structural long-period gratings. [20]

In Fig. 2 we compare the single-rod and three-rod PCFs with $d/\Lambda = 0.45$ and 0.25 , respectively. All numerical results are based on a fully-vectorial solution of Maxwell's equations in a plane-wave basis [17] and for silica we have for simplicity used $n_{\text{si}} = 1.444$. Panel (a) shows the coupling length versus wavelength. The normalization by the edge-to-edge separation $\Lambda - d$ of the air holes makes the two curves coincide at short wavelengths ($\lambda \ll \Lambda - d$) which clearly demonstrates that $\Lambda - d$ is the length scale of the fiber structure which determines the susceptibility to longitudinal modulations. Panel (b) shows the mode-field diameter as a function of wavelength and as seen the three-rod PCF provides

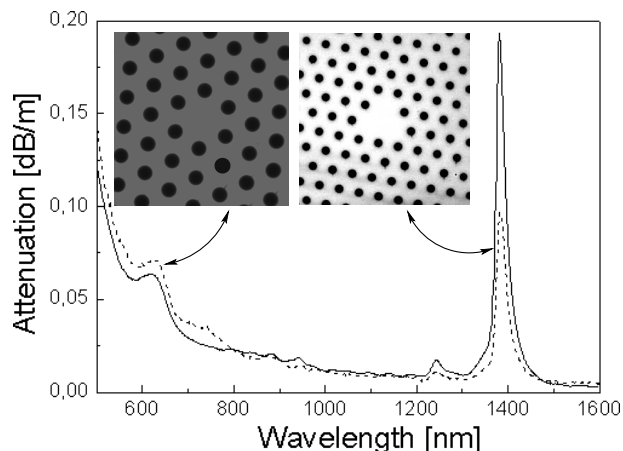


FIG. 3: Attenuation for a single-rod PCF (left insert) and three-rod PCF (right insert) fabricated under comparable conditions and both measured with a bend-radius of 16 cm. The single-rod PCF has $\Lambda \simeq 10 \mu\text{m}$, $d/\Lambda \simeq 0.45$, and a mode-field diameter around $10.5 \mu\text{m}$ whereas the three-rod PCF has $\Lambda \simeq 6 \mu\text{m}$, $d/\Lambda \simeq 0.25$, and a mode-field diameter around $12 \mu\text{m}$. Though the mode area of the three-rod PCF is enhanced by $\sim 30\%$ compared to the single-rod PCF the two types of PCFs have very similar attenuation.

a larger MFD compared to the single-rod PCF for fixed λ/Λ . Panel (c) combines the results of panels (a) and (b) in a plot of mode-field diameter versus coupling length. At $\text{MFD} \sim 7 \times \lambda$ there is a clear cross over and for

$\text{MFD} \gg \lambda$ the three-rod PCF is thus seen to be less susceptible to longitudinal modulations compared to the single-rod PCF.

Fig. 3 shows experimental results for the attenuation of both a single-rod PCF and a three-rod PCF with hole diameters ($d/\Lambda \simeq 0.45$ and 0.25 , respectively) close to the endlessly single-mode limits. The pitches are $\Lambda \simeq 10 \mu\text{m}$ and $\Lambda \simeq 6 \mu\text{m}$, respectively, so that core sizes are approximately the same. The two PCFs were fabricated by aid of the stack-and-pull method under comparable conditions and both PCFs were found to be endlessly single-mode in a wavelength range of at least 400 nm to 1600 nm. As seen the two PCFs have similar spectral attenuation even though the mode area of the three-rod PCF is enhanced by $\sim 30\%$ compared to the single-rod PCF. This demonstrate the improvement by the three-rod PCF.

In conclusion we have found that a triangular core formed by three missing neighboring air holes considerably improves the mode area and/or loss properties compared to the case with a core formed by one missing air hole. This new improved large-mode area endlessly single-mode PCF is important for high-power delivery applications and in a realized fiber we have been able to demonstrate an enhancement of the mode area by $\sim 30\%$ without a corresponding change in the loss level.

We acknowledge A. Bjarklev (Research Center COM, Technical University of Denmark) and J. Broeng (Crystal Fibre A/S) for useful discussions. M. D. N. is financially supported by the Danish Academy of Technical Sciences.

-
- [1] J. C. Knight, T. A. Birks, P. S. J. Russell, and D. M. Atkin, *Opt. Lett.* **21**, 1547 (1996).
 - [2] T. A. Birks, J. C. Knight, and P. S. J. Russell, *Opt. Lett.* **22**, 961 (1997).
 - [3] J. C. Knight, T. A. Birks, R. F. Cregan, P. S. J. Russell, and J.-P. De Sandro, *Electron. Lett.* **34**, 1347 (1998).
 - [4] J. C. Knight and P. S. J. Russell, *Science* **296**, 276 (2002).
 - [5] T. A. Birks, J. C. Knight, B. J. Mangan, and P. S. J. Russell, *IEICE Trans. Electron.* **E84-C**, 585 (2001).
 - [6] B. J. Mangan, J. Arriaga, T. A. Birks, J. C. Knight, and P. S. J. Russell, *Opt. Lett.* **26**, 1469 (2001).
 - [7] N. A. Mortensen and J. R. Folkenberg, preprint.
 - [8] M. D. Nielsen, G. Vienne, J. R. Folkenberg, and A. Bjarklev, *Opt. Lett.* in press (2002).
 - [9] T. Sørensen, J. Broeng, A. Bjarklev, E. Knudsen, and S. E. B. Libori, *Electron. Lett.* **37**, 287 (2001).
 - [10] J. Broeng, D. Mogilevstev, S. E. Barkou, and A. Bjarklev, *Opt. Fiber Technol.* **5**, 305 (1999).
 - [11] N. A. Mortensen, *Opt. Express* **10**, 341 (2002).
 - [12] B. T. Kuhlmeier, R. C. McPhedran, and C. M. de Sterke, *Opt. Lett.* **27**, 1684 (2002).
 - [13] B. J. Mangan, J. C. Knight, T. A. Birks, and P. S. J. Russell, *Electron. Lett.* **36**, 1358 (2000).
 - [14] T. P. Hansen, J. Broeng, S. E. B. Libori, E. Knudsen, A. Bjarklev, J. R. Jensen, and H. Simonsen, *IEEE Photon. Tech. Lett.* **13**, 588 (2001).
 - [15] T. P. White, R. C. McPhedran, C. M. de Sterke, L. C. Botton, and M. J. Steel, *Opt. Lett.* **26**, 1660 (2001).
 - [16] M. Koshiba and K. Saitoh, *IEEE Photon. Tech. Lett.* **13**, 1313 (2001).
 - [17] S. G. Johnson and J. D. Joannopoulos, *Opt. Express* **8**, 173 (2001).
 - [18] N. A. Mortensen and J. R. Folkenberg, *Opt. Express* **10**, 475 (2002).
 - [19] J. D. Love, *IEE Proc.-J* **136**, 225 (1989).
 - [20] G. Kakarantzas, T. A. Birks, and P. S. J. Russell, *Opt. Lett.* **27**, 1013 (2002).